

# Tobacco Plant Extracts as Environmentally Benign Corrosion Inhibitors

GUY D. DAVIS, *DACCO SCI, Inc.*

J. ANTHONY VON FRAUNHOFER, *Inhibitrol, Inc.*

Tests showed that extracts of tobacco plants are highly effective in preventing corrosion of two important metals—steel and aluminum—in saline environments. The extracts are biodegradable and environmentally benign and are obtained from a renewable resource with minimal health and safety concerns. They have the potential to be a cost-effective alternative to toxic corrosion inhibitors.

Extracts of tobacco plants are effective, environmentally friendly corrosion inhibitors. Corrosion inhibitors are compounds that are commonly added in small quantities to an environment to prevent corrosion. Because some corrosion inhibitors present environmental and health risks, there is a demand for less toxic corrosion inhibitors. Extracts from tobacco plants can be very effective in reducing the corrosion rates of several metals in saline

(chloride-containing) solutions, often resulting in a greater inhibition effect than chromates.<sup>1-3</sup> The extracts offer several advantages over chromates (which are illegal to use in the U.S.) and related inhibitors: 1) they are biodegradable and environmentally benign with minimal health and safety concerns; 2) they originate from a renewable biosource; and 3) they are cost-effective.

Tobacco plants produce ~4,000 chemical compounds—including terpenes, alcohols, polyphenols, carboxylic acids, nitrogen-containing compounds, and alkaloids<sup>4</sup>—that may exhibit electrochemical activity, such as corrosion inhibition. The many compounds present in the extract make identifying the active inhibitive components difficult, if not impossible. Consequently, the focus of this effort has been to develop an inexpensive natural extraction product that effectively inhibits corrosion.

## Corrosion Inhibition Efficacy

### INHIBITION OF GALVANIC COUPLES

Numerous types or strains of tobacco exhibit excellent corrosion inhibition. Neither the quality nor form of plant material is an important factor in inhibition efficacy. Figure 1 shows representative results. Most tobacco samples gave inhibition efficacies of more than 90%, with some as high as 99.8%. The effectiveness of the corrosion inhibition does not appear to be dependent on the quality of the tobacco. Both low-quality tobacco material (dust, scrap, and KY B005 tree tobacco) and high-quality material (Little Crittenden, VA tobacco, KY Burley leaf, NC129 Burley, and KY 171) give similar results. This finding is important because low-cost and scrap tobacco material (dust, twigs, and stems, or low-quality leaves) can be used and can be highly effective in reducing corrosion.

These data also indicate that inhibition efficacy is not limited to a specific


metal. The steel/Cu, Al/Cu, and steel/Al galvanic couples showed similar corrosion inhibition for most tobacco samples. Averaged over all tobacco samples, the corrosion inhibition efficacy is 96% for steel/Al, 90% for steel/Cu, and 79% for Al/Cu. Previous results indicate that this efficacy is equal to or better than that provided by chromates.<sup>1,3</sup> Other measurements of these metals (polarization resistance and visual inspection of immersed specimens) individually show similar results. The tobacco extract appears to be a universal corrosion inhibitor, much like chromates, and unlike other organic corrosion inhibitors that are effective for only one or two metals.

Figure 2 shows corrosion inhibition efficacy of the Burley Tobacco Dust extract at different extract concentrations for the three galvanic couples. Most of the corrosion inhibition is achieved between 0.03 and 0.1% of extract, with only small improvements at 1% or higher. Even at 0.01% (100 ppm) significant inhibition is seen, especially for the Al-containing couples. Note that the extract concentrations presented are the total concentrations of the material extracted from the tobacco material; the concentrations of the active inhibitive component(s) are unknown but are believed to be much lower.

### WEIGHT LOSS TESTS


Another means of detecting corrosion and corrosion inhibition is weight loss. Figure 3 shows the weight loss of Al and steel panels immersed in salt water with and without tobacco extract added. The inhibition of corrosion by the tobacco is clear. Inhibition efficacies of ~90% or more were obtained through the immersion time; they compare favorably with those obtained from the zero-resistance ammeter (ZRA) measurements above. The slight weight gain (negative weight loss) of the Al panel likely resulted from a thin deposit of tobacco forming on the surface of the Al.

**FIGURE 1**

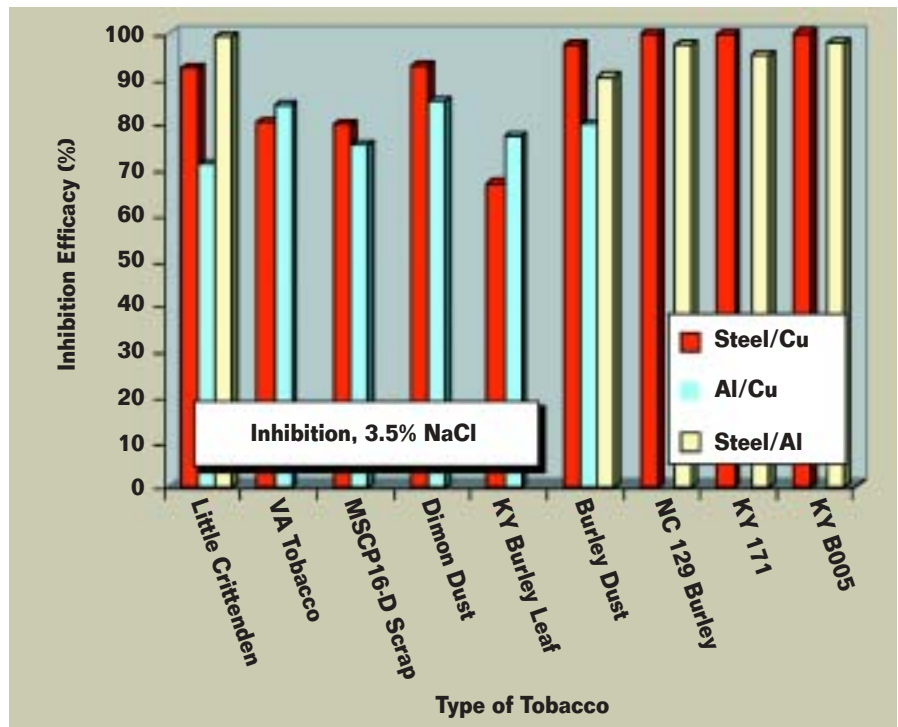

Inhibition efficacy of tobacco extracts for steel/Cu, Al/Cu, and steel/Al galvanic couples, as measured by a ZRA. Different tobacco strains and qualities are shown.

**FIGURE 2**

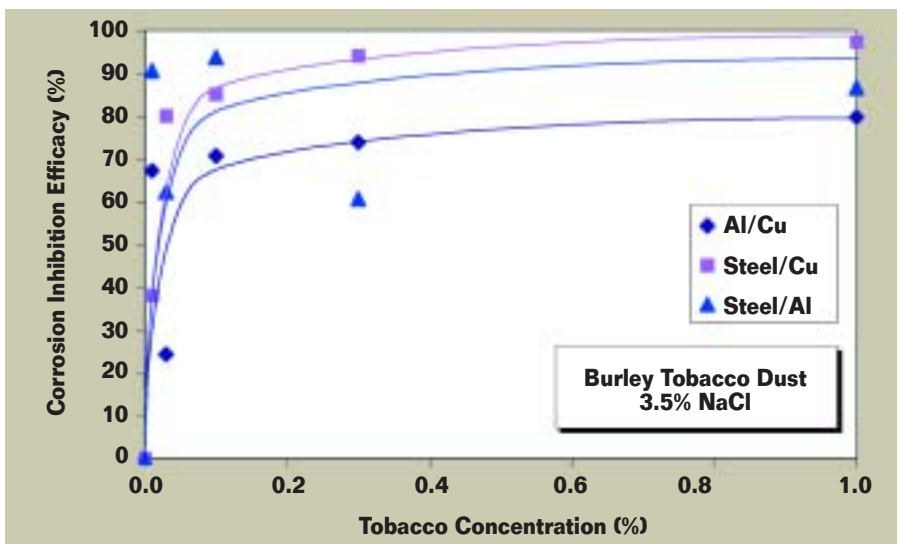


Corrosion inhibition efficacy, as determined by ZRA current measurements, for the Al/Cu, steel/Cu, and steel/Al galvanic couples immersed in salt water with different concentrations of tobacco extract.

### IMMERSION PANELS

Perhaps the most impressive visual display of corrosion inhibition by the tobacco extracts is the immersion of bare and scribed painted panels in salt

water with and without tobacco extracts. Figure 4 shows bare Al panels after 62 and 220 days. At both times (and at much earlier times), the panel in the salt water without tobacco was

**FIGURE 3**

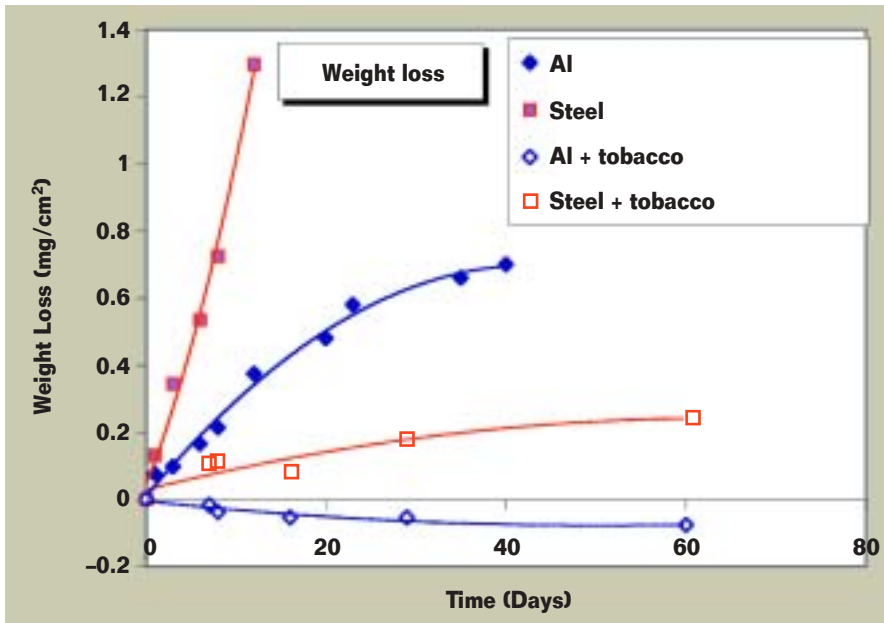

Weight loss of Al and steel panels immersed in salt water with and without tobacco extract.

heavily pitted and showed extensive corrosion. After 62 days, the Al panel in the tobacco solution was still bright and shiny. After 220 days, the panel had a thin layer of tobacco deposit. The deposit tends to give the surface a golden luster, which does not represent corrosion. First noted after 127 days, it is most pronounced in the 3% tobacco solution but occurs to a lesser extent in the 0.3% solution shown. The


220-day specimens also exhibited isolated areas of localized corrosion near the edges. These corroded areas likely resulted from a combination of cold working from the panel-forming process and inclusions in the metal. Little or no general or pitting corrosion is seen away from the panel edges.

The steel panels had similar results (Figure 5). Even after 127 days, the panel immersed in salt water plus to-

bacco extract showed very little corrosion. In contrast, the panel immersed in salt water without tobacco was heavily corroded as the corrosion began soon after the panels were immersed. As with the Al panels, a tobacco deposit formed on some of these panels—especially those with 3% tobacco extract. With the steel panels, some corrosion was observed after 220 days even with tobacco. The tobacco solution had not been replaced during this time, suggesting that some replenishment might be needed for extended periods of time.

Additional steel panels were painted with three different household primers (a water-based primer and two oil-based primers). To make the experiment as aggressive as possible and provide the most stringent test of the inhibition efficacy of the tobacco extract, no topcoat was added over the primer. Salt water solutions with both 3 and 0.3% tobacco extract concentrations were used. Both were effective, indicating that the lower inhibitor concentration is adequate for this application. With the higher inhibitor concentration, after a period of time there was a brown deposit of tobacco material on the paints. With the lower concentra-

**FIGURE 4**

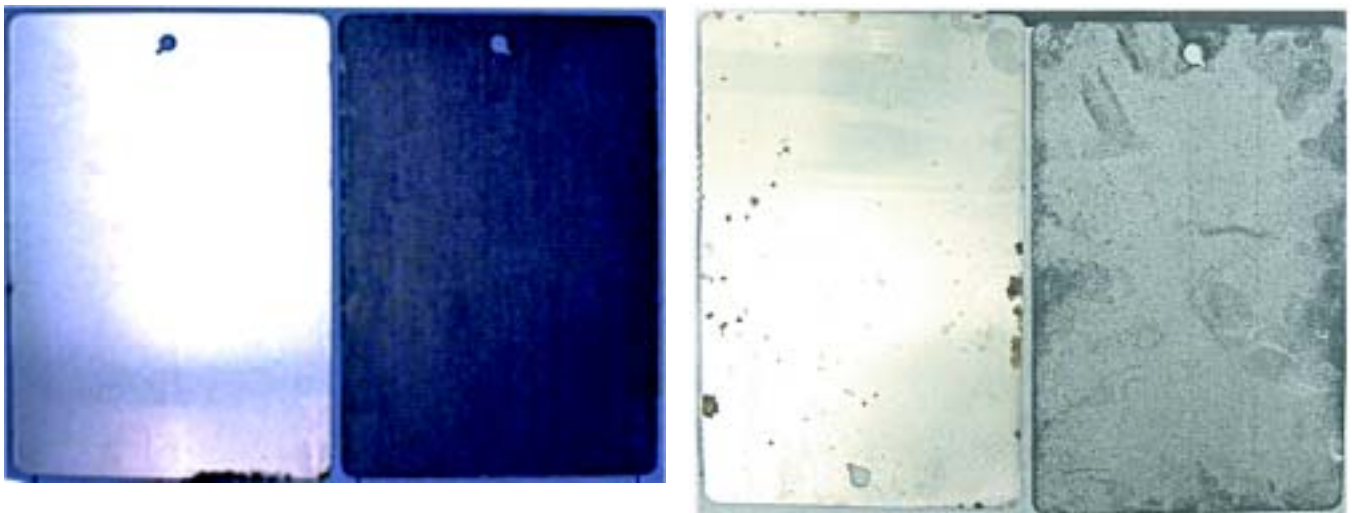

Al panels immersed in salt water with and without 0.3% tobacco extract. Left pair—after 62 days immersion. Right pair—after 220 days immersion. The left-hand panel of each pair was immersed in the tobacco-inhibited solution. The right-hand panel of each pair was immersed in the uninhibited solution.

tion, any deposit was greatly reduced—if present at all.

Figure 6 shows selected panels after 192 days of immersion. In each case, there is little or no rust from the scribes on specimens immersed in the tobacco solutions (upper pair of each set). As expected, the water-based primer (without tobacco in solution) exhibited the most rust as rust originated from the scribe within days of immersion. The oil-based primers worked better without the tobacco extracts, although there still was significant rusting at the scribed area. This rust is greatly reduced with tobacco, with almost no corrosion or undercutting observed at the scribe.

## Conclusions


Extracts of tobacco plants are very effective corrosion inhibitors in salt water. They provide corrosion protection to steel and Al and to galvanic couples of these metals with themselves or with Cu. Compared to

chromates, the extracts are environmentally benign, biodegradable, and nontoxic. Additionally, the tobacco extracts are obtained from a renewable source and can be inexpensive with the use of waste tobacco material.

## Acknowledgments


The authors thank Fernando Garra for his technical assistance. This work was funded by the U.S. Department of Agriculture under contracts 0033610-8937 and 2001-33610-110.

**FIGURE 5**

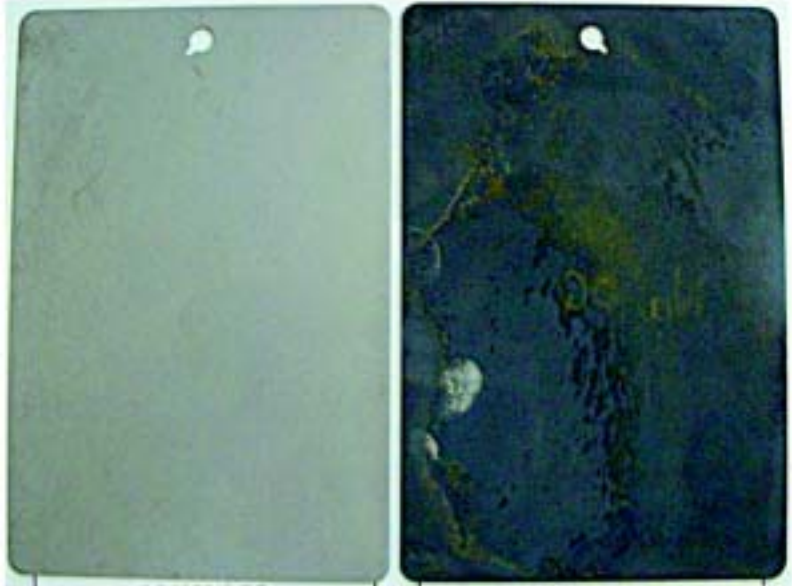

Steel panels immersed in salt water with (left) and without (right) tobacco inhibitor for 127 days.

**FIGURE 6**

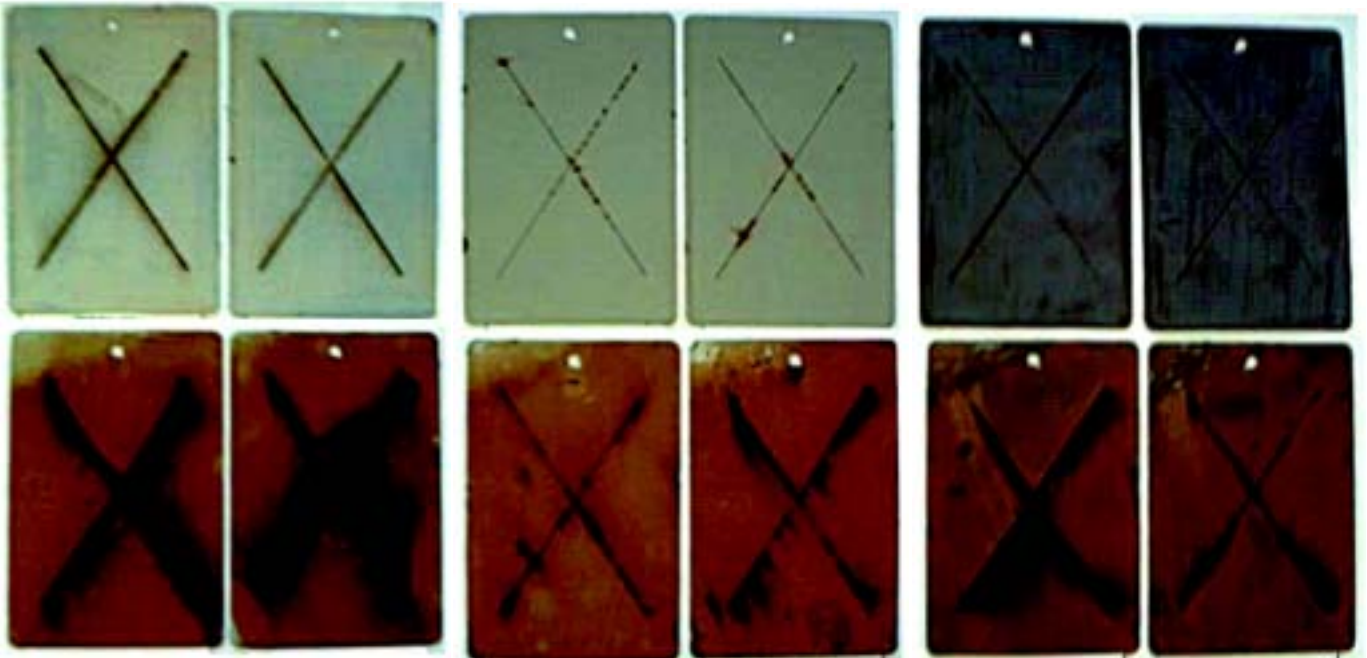

Scribed, painted steel panels immersed in salt water for 192 days. Side-by-side pairs are duplicates. Top pairs of each set were immersed in the salt + tobacco solution. Bottom pairs of each set were immersed in the salt solution without tobacco. Left—water-based primer. Center—oil-based primer #1. Right—oil-based primer #2.

# "STAPERM"

PERMANENT

REFERENCE

ELECTRODES BY

THE WORLD

LEADER

IN R & D

Meticulously engineered and manufactured to uncompromising quality standards for a complete range of corrosive environments in salt water, fresh water, waste water, underground and bridge deck applications.

**GMC ELECTRICAL, INC.**  
CORROSION CONTROL EXPERTS

2132-F GROVE AVE., ONTARIO, CA 91761, USA

**(909) 947-6016**

**FAX (909) 947-9430**

[www.staperm.com](http://www.staperm.com)

[www.gmcelectrical.com](http://www.gmcelectrical.com)

# CT Chemical Treatment

## References

1. J.A. von Fraunhofer, Tobacco Extract Composition and Method, U.S. Patent 5,435,941 (1995).

2. J.A. von Fraunhofer, Advanced Materials and Processes 158, 33 (2000).

3. G.D. Davis, J.A. von Fraunhofer, L.A. Krebs, C.M. Dacres, "The Use of Tobacco Extracts as Corrosion Inhibitors," CORROSION/2001, paper no. 558 (Houston, TX: NACE, 2001).

4. World Health Organization, IARC Monographs on the Evaluation of the Carcinogenic Risk of Chemicals to Humans. Volume 37: Tobacco Habits Other Than Smoking; Betel-Quid and Areca-Nut Chewing; and Some Related Nitrosamines, International Agency for Research on Cancer, September 1985.

GUY D. DAVIS is a Principal Scientist at DACCO SCI, Inc., 10260 Old Columbia Road, Columbia, MD 21046. His research interests include adhesive bond formation and durability, adherent surface preparation, corrosion and corrosion inhibition/protection, and the nondestructive detection of

corrosion of painted and bonded structures. He has a Ph.D. in materials science from the University of Wisconsin-Madison. He received the William Blum Award from the Electrochemical Society and is a Robert L. Patrick Fellow of The Adhesion Society, Fellow of the American Vacuum Society, and Fellow of ASM International.

J. ANTHONY VON FRAUNHOFER is with Inhibitrol, Inc., 11867 Sherbourne Drive, Timonium, MD 21093. He is a Professor and Director of Biomaterials Science, School of Dentistry, University of Maryland. He has an honors degree from the University of London and M.Sc. and Ph.D. degrees in metallurgy. His research interests include the biomechanical properties of materials used in medicine and dentistry; suture materials and wound closure devices; wound healing and bone; degradation, wear, and corrosion of materials in the biosystem; and the corrosion and corrosion protection of metals by organic and metallic coatings. He has published more than 300 scientific papers, 10 books, and 11 book chapters. *MP*

# Simple. Durable. Accurate.

COATING THICKNESS GAGES  
FOR ALL METAL SUBSTRATES

## PosiTector® 6000 Series

**SIMPLE** – Automatic Gage Setup and two-button operation allow you to take basic measurements or perform advanced functions easily. **Now with a larger, easier to read LCD and menu-driven user interface.**

**DURABLE** – Tough Probes, Robust Housing, Strong Warranty... the PosiTector 6000 is made to measure in rugged environments. Unaffected by vibration, this heavy-duty gage also resists exposure to solvents, acids, oil, water and dust.

**ACCURATE** – Measuring with High Resolution and Accuracy, each quality-tested PosiTector 6000 gage leaves our facility with a Certificate of Calibration providing traceability to NIST.

Learn about the upgraded PosiTector  
at 1-800-448-3835 or [www.defelsko.com](http://www.defelsko.com)

**DeFelsko®**  
CORPORATION

DEFELSKO CORPORATION, 802 Proctor Avenue  
P.O. Box 676, Ogdensburg, New York 13669  
Phone: 315-393-4450 • Fax: 315-393-8471

Advanced  
**New**  
Features!



# How thick is it and how much longer will it last?

## From measure to verify to document to analyze...

Agfa NDT has the tools you need with the Krautkramer line of Ultrasonic Thickness Gauges, Probes and Software.

- Basic, reliable thickness readings with the DM4 and DMS 2 Thickness Gauges
- Probes to meet any application requirement
- Measure through coatings, save time and money with DM4 dual-multi and Patented DMS 2 TopCOAT (US Pat 6035717)
- Visualize cross-sections with DMS 2 B-Scans
- Electronically store readings, A-Scans, B-Scans and comments on DMS 2 Data Recorder
- Document and report results with easy to use UltraMATE Software
- Predict remaining life, manage mechanical integrity and maintain complete inspection documentation with UltraPIPE Software

### Everything you need from one source.

Contact your Krautkramer Ultrasonic Systems Sales Representative, or visit our web site [AgfaNDT.com](http://AgfaNDT.com) to see our entire line of Non-destructive Testing products.

 **Krautkramer**  
Ultrasonic Systems

Agfa NDT Inc.  
50 Industrial Park Road  
Lewistown, PA 17044  
PH: (717) 242-0327 FAX: 717-242-2606  
Email: [infolink@agfandtinc.com](mailto:infolink@agfandtinc.com)

[AgfaNDT.com](http://AgfaNDT.com)

A WORLDWIDE RESPONSE

**AGFA** 

Visit us at NACExpo/2003 Booth 1200!